

RESEARCHES REGARDING STRUCTURAL CHANGES DUE TO NICKEL MICROLLOYING OF HOT GALVANIZING BATHS

Radu BOICIUC¹, Adriana PREDA¹,
Simona BOICIUC²

¹ S.C. Uzinsider Engineering S.A. Galați,
² "Dunărea de Jos" Galați University
e-mail: boiciuc.simona@ugal.ro

ABSTRACT

This work offers a synthesis of researches performed in laboratory and regards the nickel microalloying of hot galvanizing baths. Experiments followed the structural changes of both hot galvanizing bath and deposited layer with effect on layer properties.

Characterization of deposited layer and nickel microalloying of galvanizing bath performed by spectral chemical analysis, optical microscopy and X ray diffraction emphasized the structural constituents nature as well as changes shown up depending on nickel concentration of galvanizing bath. Correlation diagrams between deposited layer thickness and structural constituents were also made.

Experimental results emphasized a close interdependence between nickel concentration and microstructure. This allowed to settle the optimal nickel concentration required by galvanizing bath microalloying with maximum effect upon hot galvanizing coating properties.

1. Generals

Experiments performed on a pilot plant used A5K steel strip (as per STAS 10.318) or A35 – 401 type (according to ZE French standard) and included coating by hot galvanizing of several samples (P₁-P₇ code) suitable for the following nickel concentrations in galvanizing bath: 0%; 0,02%; 0,06%; 0,09%; 0,11%; 0,16% and 0,20%.

Galvanizing technology used is the classical one. Samples were degreased, pickled, preheated for 30

seconds, immersed in galvanizing bath for 60 seconds and then freely cooled in air.

2. Spectral chemical composition of deposited layer

Spectral chemical analysis on coating layer performed by Baird DV 6 optical emission spectrometer got the results included in table no.1.

Table no.1 – Spectral chemical composition (%) of samples galvanized and microalloyed by nickel

Sample code	Ni	Fe	Cu	Pb	Sn	Cd
P₁	0	4.651	0.000	0.001	0.004	0
P₂	0.02	1.599	0.001	0.001	0.008	0.001
P₃	0.06	0.412	0.001	0.001	0.005	0.001
P₄	0.09	0.264	0.001	0.001	0.005	0.001
P₅	0.11	0.177	0.001	0.001	0.003	0.001
P₆	0.16	0.168	0.001	0.001	0.002	0.001
P₇	0.20	0.163	0.001	0.001	0.002	0.001

It may be seen an important decrease of Fe content in the coating layer in the same time with increasing the degree of bath microalloying up to 11% nickel content.

Over this value the Fe content will stay approximate constantly.

Methallographic analysis performed by Olympus microscope, endowed by data acquisition automatic system, on specimens sampled from galvanized steel sheets and galvanizing bath.

Measurements results are given in table no.2.

3. Structural methallographic determinations

Table no. 2. Thickness of zinc layer and intermetallic layers

Sample code	Zn layer thickness (eta) [μm]						Intermetallic composes layer thickness [μm]					
	g_1	g_2	g_3	g_4	g_5	G_{mZn}	g_6	g_7	g_8	g_9	g_{10}	g_{mCmet}
P₁	31.64	32.52	30.77	29.10	29.84	30.77	48.35	49.77	48.52	50.25	50.11	49.40
P₂	46.61	42.19	48.41	48.34	46.59	43.43	37.55	34.89	37.07	35.16	36.93	36.32
P₃	58.89	57.16	56.87	58.02	58.89	57.96	15.85	15.82	15.81	15.26	15.82	15.71
P₄	61.73	60.68	60.65	60.65	61.54	61.05	14.85	15.59	15.49	15.94	15.77	15.53
P₅	71.19	71.24	71.22	71.19	70.95	71.16	15.70	15.33	15.78	15.43	15.20	15.48
P₆	69.25	69.34	70.11	70.08	69.53	69.66	15.82	15.27	15.84	15.83	15.83	15.72
P₇	70.34	70.86	70.64	71.48	71.20	70.84	20.21	19.13	20.23	20.21	20.19	19.99

Note: g_m – the average value of deposited layer

Analyzing the results it may be remarked that changes of deposited layers thickness took place depending on Ni percentage added in the bath.

Up to 11% Ni content inside bath the Zn layer thickness increase and intermetallic compounds layer thickness

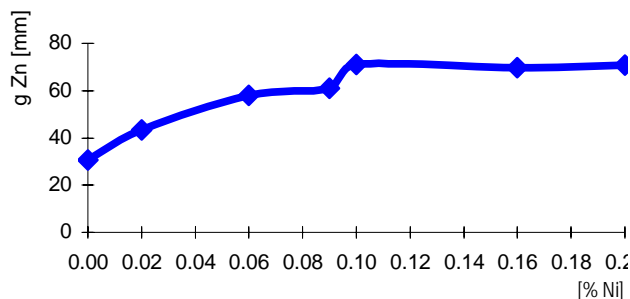


Fig. no.1. Variation of Zn layer thickness depending on Ni content of metallic bath

decrease are recorded. Over this value the deposited layers thickness is kept approximately steady and it is a relevant aspect on diagrams in figures no.1 and 2.

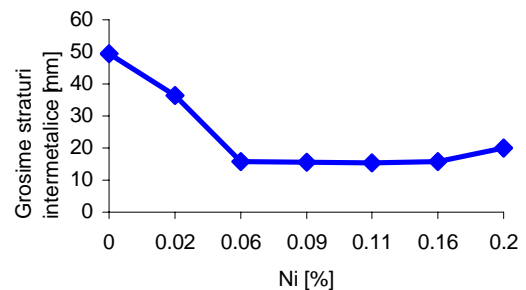


Fig. no.2. Variation of intermetallic compounds layer thickness depending on Ni content of metallic bath

Gradually by increasing the nickel microalloying degree of galvanizing bath, metallographic analysis emphasized (figures no. 3÷6) important changes in deposited layer structure:

- Finishing of Zn grains and apparition of Ni-Zn intermetallic compound disperse particles in eta layer;
- Decreasing and finishing the layer in "palisade";

- Coalescence of Ni-Zn intermetallic compound particles precipitated in eta layer.

Metallic bath microalloying by nickel, even in very small concentrations, made essential changes of its microstructure (Fig. no. 7÷12).

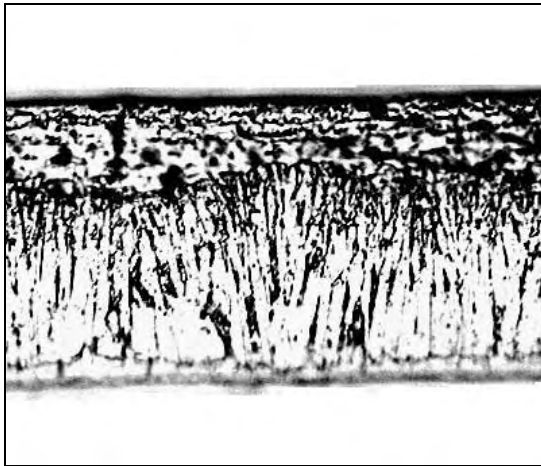


Fig. no. 3 Microstructure of deposited layer,
0 % Ni. (x 500). 1% nital attach.

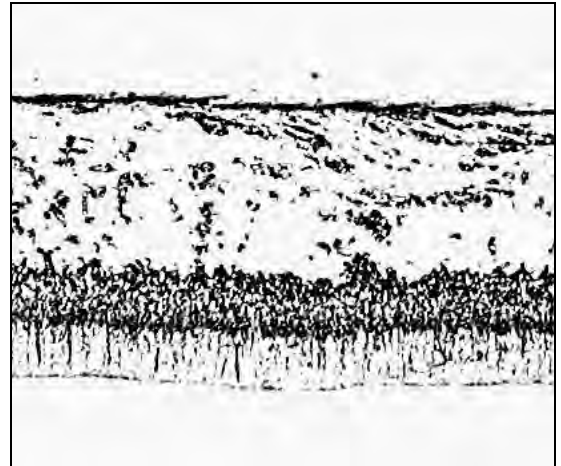


Fig. no. 4 Microstructure of deposited layer,
0.06 % Ni. (x 500). 1% nital attach.

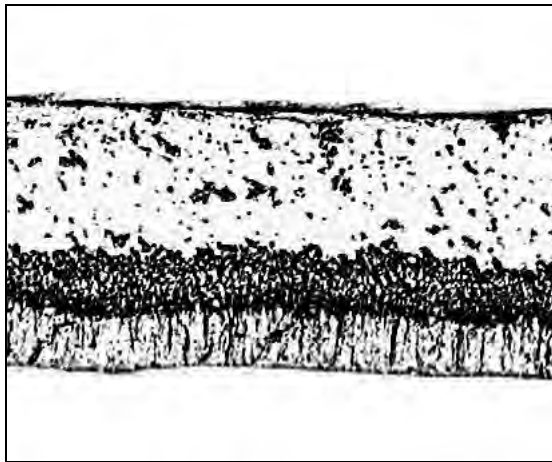


Fig. no. 5 Microstructure of deposited layer,
0.11 % Ni. (x 500). 1% nital attach.

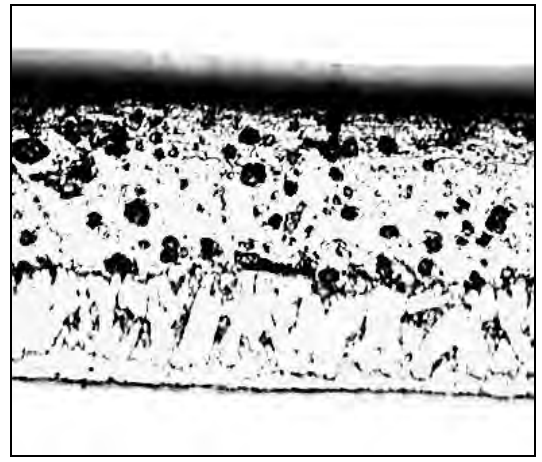


Fig. no. 6 Microstructure of deposited layer,
0.20 % Ni. (x 500). 1% nital attach.



Fig. no. 7 Microstructure of the bath 0 % Ni.
(x 100). 1% nital attach.
Zn large crystals with macles.

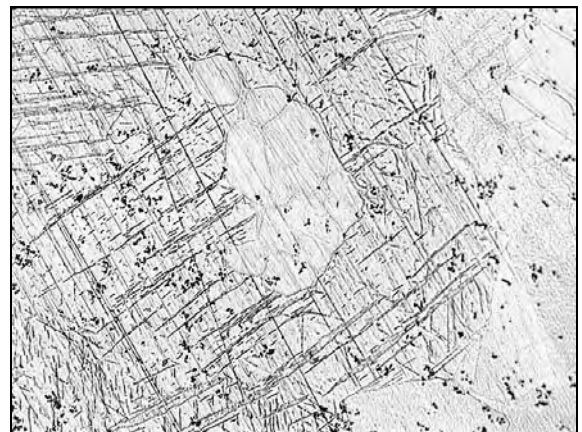


Fig. no. 8 Microstructure of the bath 0,02 % Ni.
(x 100). 1% nital attach.
Zn large crystals with tendency to form Zn-Ni eutectic.

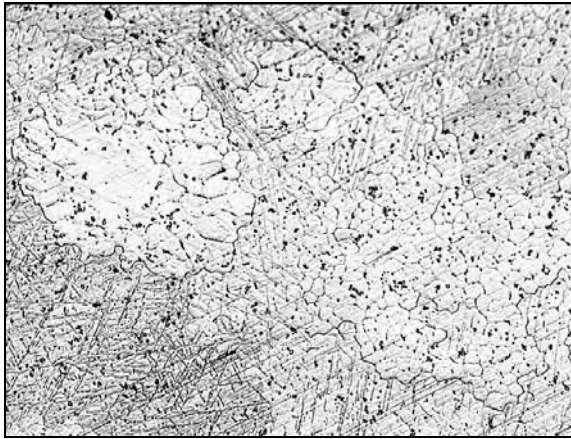


Fig. no. 9. Microstructure of the bath 0,06 % Ni (x 100). 1% nital attach. Inhomogeneous eutectic structure in which very fine dispersed particles of Ni-Zn intermettalic compound show up.



Fig. no. 10. Microstructure of the bath 0,09 % Ni. (x 100). 1% nital attach. Eutectic structure in which fine dispersed particles of Ni-Zn intermettalic compound show up.

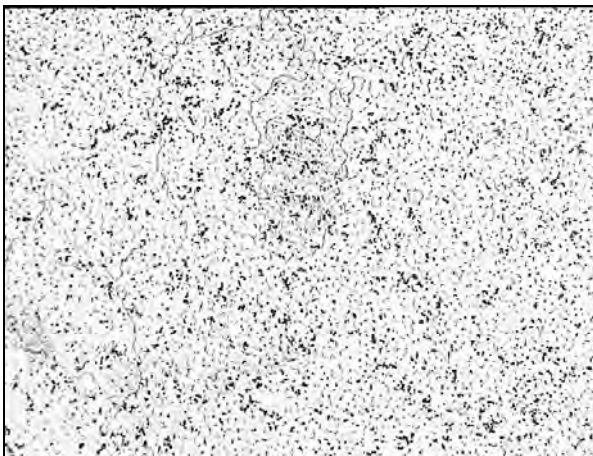


Fig. no. 11. Microstructure of the bath 0,11 % Ni. (x 100). 1% nital attach. Fine eutectic structure in which fine particle agglomeration of Ni-Zn intermettalic compound show up dispesed.

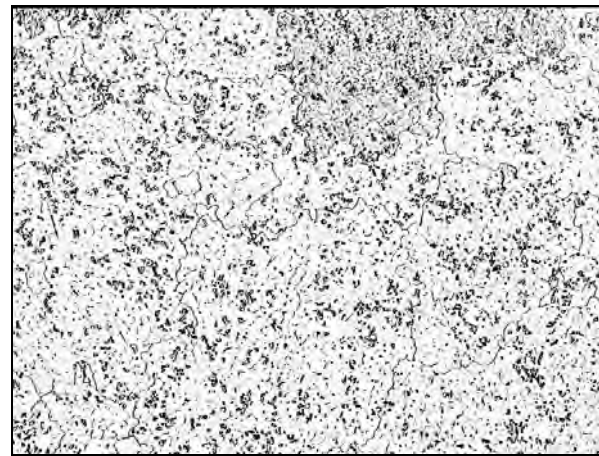


Fig. no. 12. Microstructure of the bath 0,20 % Ni. (x 100). 1% nital attach. Fine eutectic structure in which globular particle agglomeration of Ni-Zn intermettalic compound show up.

Large Zn crystals grained in the same time with Ni content increasing up to a very fine eutectic structure where the Ni-Zn intermetallic compound particles precipitated. Coalescence and crowding of these particles made in the same time with alloying percentage increasing. X ray diffractometric analysis confirmed the results got by both spectral chemical and metallographical analysis .

Phases identified in metallic layer were

- (γ) gamma adherence layer : $\text{Fe}_5\text{Zn}_{21}$;
- (δ) delta frail layer in "palisade" : FeZn_7 ;
- (ξ) zeta intermediary layer - $\text{Fe}_3\text{Zn}_{10}$;

- (η) eta layer or pure Zn;
- NiZn_3 intermetallic compound.

Quantitative ratio of the first four phases varies depending on Ni content up to $\text{Fe}_3\text{Zn}_{10}$ intermediary phase vanishing.

NiZn_3 intermetallic compound apparition was signaled in the same time with feeding the Ni in metallic bath, its quantitative ratio increasing direct proportional by this element content recording a level inside $0.11 \div 0.16\%$ Ni range (fig. no. 13).

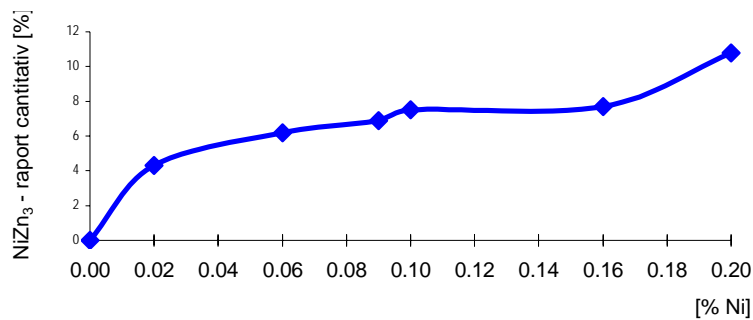


Fig. no. 13. Variation of NiZn₃ phase quantitative ratio depending on Ni content of metallic bath

Fine structure additionally hardened by NiZn₃ intermetallic compound, dispersed in pure zinc in quantitative ratio up to 10.8%, confers special resistance and corrosion properties.

4. Conclusions

Nickel microalloying of hot galvanizing bath determines essential changes of both bath and deposited layer microstructures.

Fe content decreases by Ni content increasing up to 0.11 % as a result of Fe_xZn_y type layers decreasing and apparition of NiZn₃ compound.

Eta zinc layer thickness increases by 131% and that one of intermetallic layers decreases by 69% Ni in galvanizing bath. Over this value thickness stays steadily.

Deposited layer structure records the following changes:

- Decreasing and finishing the layer in "palisade";
- Finishing of Zn grains and apparition of disperse particles of Ni-Zn intermetallic compound in eta layer;
- Coalescence of Ni-Zn intermetallic compound particles precipitated in eta layer.

Large Zn crystals grained in the same time with Ni content increasing up to a very fine eutectic.

NiZn₃ intermetallic compound presence in deposited layer, in a quantitative ratio of up to 7.5% suitable for 0.11% Ni content determines both structure finishing and additional hardening of coating with maximum effects on coating quality.

References

- [1]. G. Reumont, P. Perrot, J. Foct - *Thermodynamic study of the galvanizing process in a Zn – 0,1 % Ni bath*, Journal of Materials Science 33, pg. 4759-4768, 1998.
- [2]. G. P. Lewis, J. Pederson - *Optimizing the Ni-Zn process for hot dip galvanizing*, Cominco LTD., 1998
- [3]. C. Alonso, J. Sanchez, J. Fulla, C. Andrade, P. Tierra, M. Bernal - *The addition of nickel to improve the corrosion resistance of galvanized reinforcement*, 1995
- [4]. D. Stroud - *Galvanizing with Zn-Ni alloy*, Proceedings first Asian-Pacific General Galvanizing Conference, Taiwan, 1992